

Polymer Nanocomposites

Karen I. Winey and Richard A. Vaia,
Guest Editors

Abstract

Polymer nanocomposites (PNCs)—that is, nanoparticles (spheres, rods, plates) dispersed in a polymer matrix—have garnered substantial academic and industrial interest since their inception, circa 1990. This is due in large part to the incredible promise demonstrated by these early efforts: PNCs will not only expand the performance space of traditional filled polymers, but introduce completely new combinations of properties and thus enable new applications for plastics. Low volume additions (1–5%) of nanoparticles, such as layered silicates or carbon nanotubes, provide property enhancements with respect to the neat resin that are comparable to those achieved by conventional loadings (15–40%) of traditional fillers. The lower loadings facilitate processing and reduce component weight. Most important, though, is the unique value-added properties not normally possible with traditional fillers, such as reduced permeability, optical clarity, self-passivation, and increased resistance to oxidation and ablation. These characteristics have been transformed into numerous commercial successes, including automotive parts, coatings, and flame retardants. This issue of the *MRS Bulletin* provides a snapshot of these exemplary successes, future opportunities, and the critical scientific challenges still to be addressed for these nanoscale multiphase systems. In addition, these articles provide a perspective on the current status and future directions of polymer nanocomposite science and technology and their potential to move beyond additive concepts to designed materials and devices with prescribed nanoscale composition and morphology.

Introduction

Polymers have been a part of life since the beginning of humankind. From tar and shellac, tortoise shell and horns, to today's synthetic offerings such as polyolefins, epoxies, and engineering resins, polymers provide crucial materials for construction, commerce, transportation, and entertainment across the globe. Estimates of global polymer production range from 250 billion pounds to more than 400 billion pounds (approximately 114–181 billion kg) annually.

In the majority of their diverse applications, polymeric materials are not chemically or molecularly homogenous but are multicomponent systems. By adding fillers, such as minerals, ceramics, metals, or even air, materials scientists can generate an infinite variety of materials with unique physical properties and competitive production costs. For example, adding filler to a commodity thermoplastic such as polypropylene can achieve performance levels that would otherwise require a much more

expensive engineering plastic. Similarly, combining different polymers to form a polymer blend or resin can increase the value of existing polymers.

Polymer nanocomposites incorporate a new spectrum of fillers that extend the function and utility of polymers while maintaining the manufacturing and processing flexibility inherent to plastics, thermosets, and resins. In particular, polymer nanocomposites have been successful with regard to overcoming traditionally antagonistic combinations of properties.

Since the first reports in the late 1980s,^{1–6} the term “polymer nanocomposite” has evolved to refer to a multicomponent system in which the major constituent is a polymer or blend thereof and the minor constituent has at least one dimension below 100 nm. Polymer nanocomposite is an appropriate synonym for inorganic–organic hybrids and molecular composites and also encompasses mature commercial products

such as polymers containing carbon black or fumed silica. This issue of *MRS Bulletin* focuses primarily on polymer nanocomposites containing nanoscale clays and various carbon nanotubes to illustrate the status of this rapidly evolving research and development enterprise.

The numerous reports of large property changes with very small additions of nanoparticles (<1–5 wt%) have fueled the view that nanoparticles are a magic pixie dust that delivers huge dividends. In fact, recent market surveys have estimated global consumption of polymer nanocomposites at tens of millions of pounds (~\$250 million), with a potential annual average growth rate of 24%, to almost 100 million pounds in 2011 at a value exceeding \$500–800 million.^{7–9} Major revenues are forecast from large commercial opportunities such as automobile parts, coatings, flame retardants, and packaging, where lower-cost, higher-performance materials would improve durability and design flexibility while lowering unit price and life cycle cost.

Whatever the case for the long-term economic growth of polymer nanocomposites, the opportunities to deliver targeted material performance reside with the implications associated with nanoscale multiphase systems. There are important differences when the fillers shrink from microscale to nanoscale. This issue of the *MRS Bulletin* provides a snapshot of exemplary successes, future opportunities, and the critical scientific challenges still to be addressed for these nanoscale multiphase systems. In addition, these articles provide a perspective on the current status of polymer nanocomposite science and technology as well as future directions to move it beyond additive concepts to designed materials and devices with prescribed nanoscale composition and morphology.

The Nano Advantage

When fillers are nanoscopic, there are advantages afforded to filled polymers and composites that lead to performance enhancements. These advantages result primarily from filler size reduction and the concomitant increase in surface area. The size of the additive might drop by up to three orders of magnitude relative to conventional alternatives. In contrast, many nanotechnologies associated with electrical or optical properties benefit from new physical phenomena arising from quantum confinement effects induced by the nanoscale dimensions of the material. The literature about polymer nanocomposites contains many discussions about the implications and physical manifestations of the reduction in filler length scale.^{10–14}

For example, compare a microcomposite and a nanocomposite with the same volume fraction of a secondary constituent (filler), where the spherical particles have volumes of $1 \mu\text{m}^3$ or 1nm^3 per particle, respectively. The mean particle-particle separation is smaller by three orders of magnitude, the total internal interfacial area increases by six orders of magnitude, and the number density of constituents increases by nine orders of magnitude in the nanocomposite. Although these numbers alone are impressive, the filler size must be viewed relative to the size of polymer molecules to capture the full potential impact of nanoscale fillers on composite properties.

Many properties are related to the size of the polymer chain, which can be expressed as the radius of gyration R_g (the second moment of the three-dimensional distribution of the monomers of the polymer chain—approximately the expanse of the molecule). R_g is on the order of 3–30 nm. Depending on the strength of interaction between the filler surface and the matrix, the polymer chains in close proximity to the filler will be perturbed with respect to those in the bulk (i.e., away from the interface). The thickness t of this interfacial region that surrounds the particle is, to first order, independent of the size of the particle. Thus, as the particle size decreases, the relative volume of this interfacial material, $V_{\text{interface}}/V_{\text{particle}}$, with respect to the volume of the particle, V_{particle} , will increase.

Figure 1 shows this ratio, $V_{\text{interface}}/V_{\text{particle}}$, as a function of particle aspect ratio from plates (aspect ratio <1) to spheres to rods (aspect ratio >1). The filler size is expressed as δ , the ratio of the thickness of the interface to the smallest dimension of the particle. Micrometer-sized fillers have $\delta \sim 0.01$, so that at any aspect ratio, the volume of the particles exceeds that of the interfacial region. However, when the fillers are reduced to the nanoscale and $\delta \sim 1$ –10, the volume of the interfacial region exceeds the volume of the particle. In addition, at a fixed value of δ , the aspect ratio has an effect on $V_{\text{interface}}/V_{\text{particle}}$, showing an expected increase from plates to rods to spheres as the fillers change from two-dimensional (plate) to one-dimensional (rod) to zero-dimensional (sphere) objects. The magnitude of this change increases dramatically as the filler size drops; for example, at $\delta = 10$, $V_{\text{interface}}/V_{\text{particle}}$ increases by two orders of magnitude between plates and spheres.

Furthermore, these calculations demonstrate the impact that even a small volume fraction of filler has on the surrounding polymers. For example, by dispersing a mere 1 vol% of a nanosphere (radius $\sim 2 \text{nm}$) in a polymer (interfacial thickness $\sim 6 \text{nm}$), the volume fraction occupied by

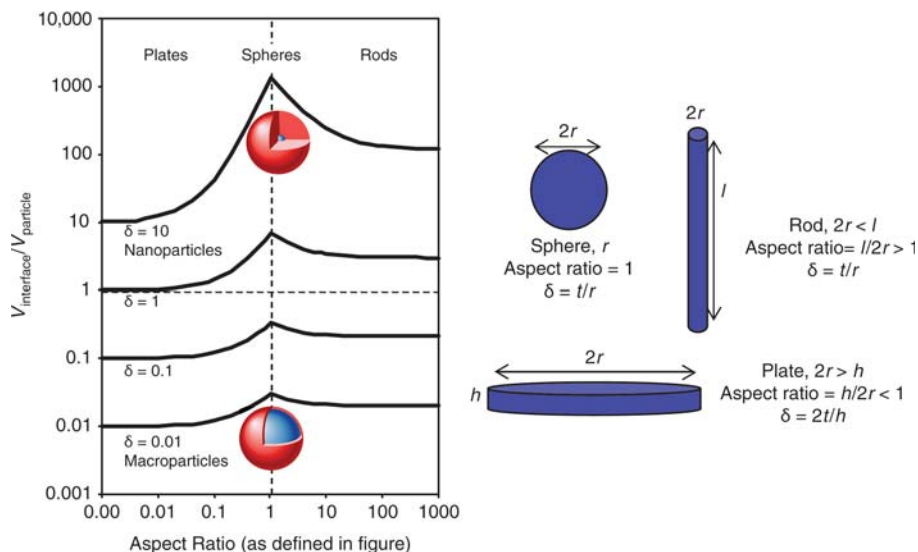


Figure 1. The ratio of interfacial volume to the particle volume ($V_{\text{interface}}/V_{\text{particle}}$) as a function of the particle aspect ratio and the ratio of the interfacial thickness to the particle size (δ). The aspect ratio and δ are defined in the schematic at right (r is radius, l is height). The interfacial thickness (red shell, t) is assumed to be independent of the particle size. As particles decrease in size to less than 100 nm, the interfacial volume around a particle can dominate the physical properties, and this is particularly evident for spheres and rods.

the interfacial region is $\sim 63 \text{ vol}\%$, suggesting that more than half of the composite is affected by the presence of the second-phase particles. If the particle is increased to 20 nm in radius without changing the interfacial thickness or particle loading, the volume occupied by the interfacial region would be only $\sim 1.2 \text{ vol}\%$.

The importance of polymer-particle interactions is amplified in polymer nanocomposites such that the interface and the cooperativity between particles dominate the macroscopic properties. For example, weak forces between particles, such as van der Waals, are more pronounced for nano-sized particles because of lower surface roughness, smaller average particle separations, and thus higher dispersive forces. Also, because of the nanoscopic dimensions of the particles, the accessible aspect ratio of discrete secondary constituents can approach 100 or more. These high-aspect-ratio, nanoscale fillers can reach percolation thresholds at <1 –5 vol% and thereby exhibit large increases in bulk mechanical and transport properties at these low loadings. The percolation threshold is the filler concentration at which the electrical conductivity increases sharply by orders of magnitude, indicating that conductive pathways span the macroscopic sample. Thus, the casual observation that nanofillers act as pixie dust is firmly rooted in the implications of reducing the size of the fillers by up to three orders of magnitude.

Scope and Impact

As with traditional filled plastics, an infinite variety of possible polymer-nanoparticle combinations conceptually affords tunability. Thus, given the diversity of possible properties and tolerable costs, there is no universal “best” nanoparticle filler for polymer nanocomposites. The best nanoparticle filler (or traditional filler, for that matter) is determined by meeting both a specific set of physical properties and a price point associated with a particular part or product. Table I compares the size, shape, properties, and uses of traditional fillers and newer nanoscale fillers. As noted earlier, a few traditional fillers have sizes below 100 nm, and nanoscale fillers can access high aspect ratios. Although there is considerable overlap in the elastic moduli and thermal conductivities between the traditional and nanoscale fillers, the electrical properties of the carbon-based nanofillers are in a class by themselves, with conductivities more than 100 times higher. This summary of fillers encourages one to imagine many possibilities for remarkable properties within the broad materials class of polymer nanocomposites.

The first key demonstration of polymer nanocomposites was provided by the pioneering work of Okada and co-workers at Toyota Central Research in the late 1980s.^{1–4} By combining inclusion and colloidal chemistry of mica-type layered silicates (nanoclay) with surface-initiated

Table I: Characteristics of Traditional and Nanoscale Fillers: Shape, Size, Properties, Dimensions, and Uses.

	Approximate Shape ^a	Smallest Dimension (nm) ^a	Aspect Ratio ^b	Elastic Modulus (GPa)	Electrical Conductivity (S/cm)	Thermal Conductivity (W/m K)	Commercial Uses
Traditional Fillers							
Carbon black ³²	agglomerate of spheres	10–100	1–5	...	10–100	0.1–0.4	tires, hoses, shoes, elastomers
Carbon fiber ³³	rods	5,000–20,000	10–50	300–800	0.1–10	100–1000	aerospace, automotive, marine, sporting, medical
Carbon graphite ³⁴	plate	250–500	15–50	500–600	1–10	100–500	gaskets, seals
E-glass ³⁵	rod	10,000–20,000	20–30	75	marine, automotive, construction, filtration
Mineral: CaCO ₃ ³⁶	sphere platelet	45–70 600–4,000	~1 1–30	35	...	3–5	paper, paint, rubber, plastics
Mineral: silica ^{37,38}	agglomerate of spheres	8,000–30,000	5–10	30–200	...	1–10	reinforced plastics, thermal insulator, paint, rubber reinforcing agent
Mineral: talc, china clay ^{37,39}	platelet	5,000–20,000	5–10	1–70	...	1–10	paper, consumer goods, construction
Nanoscale Fillers							
Carbon nanofiber ⁴⁰	rod	50–100	50–200	500	700–1000	10–20	hoses, aerospace, ESD/EMI shielding, adhesives
Carbon MWNT ⁴¹	rod	5–50	100–10,000	1,000	500–10,000	100–1000	automotive, sporting, ESD/EMI shielding
Carbon SWNT ⁴²	rod	0.6–1.8	100–10,000	1,500	1000–10,000	1000	filters, ESD/EMI shielding
Aluminosilicate nanoclay ⁴³	plate	1–10	50–1000	200–250	...	1–10	automotive, packaging, sporting, tires, aerospace
Nano-TiO ₂ ^{37,44}	sphere	10–40	~1	230,000	10 ⁻¹¹ –10 ⁻¹²	12	photocatalysis, gas sensors, paint
Nano-Al ₂ O ₃ ^{37,45}	sphere	300	~1	50	10 ⁻¹⁴	20–30	seal rings, furnace liner tubes, gas laser tubes, wear pads

^a Dispersible unit.^b Aspect ratio is defined as the long axis to short axis irrespective of shape. Note that this differs from Figure 1.

ESD is electrostatic discharge; EMI is electromagnetic interference; MWNT is multiwall carbon nanotube; SWNT is single-wall carbon nanotube.

polymerization, they demonstrated that only ~2–4 vol% of layered silicate sufficiently improved the mechanical properties of nylon-6 polymer at elevated temperatures to enable its use inside an automotive engine compartment.

Since then, the patent and literature activity has been astonishing (Figure 2).¹⁵ From 1992 to 2004, the number of citations for polymer nanocomposites has doubled every two years, indicating that these materials are still on the steep part of the technology S-curve (Figure 2a). Since 2001, polymer nanocomposites represent ~43% of the broader nanocomposite field, which includes metals, ceramics, and thin films (Figure 2b). Of the publicly available literature on polymer nanocomposites, the majority (80%) is in peer-reviewed journals, whereas patents have maintained a constant fraction (8–10%). Together, layered silicates (nanoclays) and carbon nanotubes represent almost 50% of the ongoing investigations. Polymer-clay nanocomposites, however, might be reaching saturation, as evidenced by a diminishing growth rate in publications and patents per year. In contrast, polymer-carbon nanotube composites have rapidly accelerated since the availability of carbon nanotubes became widespread in the late 1990s and are still exhibiting a steady growth rate (Figure 2b).

After almost 20 years, the diversity in scientific investigations, technology advancements, processing innovations, and product development is staggering. A significant number of excellent review papers (e.g., clays^{16–23} and carbon nanotubes^{22–26}) and books^{27–30} are available that chronicle and summarize the status of various nanoparticle-polymer combinations and the broad scientific and technological challenges that still need to be overcome.

This issue of *MRS Bulletin* provides six articles to illustrate the breadth of activity in polymer nanocomposites. Hunter et al. highlight the issues in polymer-nanoclay composites, where the most commercial activity currently exists. Baur and Silverman consider the opportunities in adding nanofillers to traditional engineering polymer composites that use continuous fiber reinforcements. Schadler and co-workers focus on the implications and engineering possibilities of larger interfacial areas per unit volume. Krishnamoorti addresses the issues of weak forces becoming significant for nano-sized components and strategies for overcoming their tendency to agglomerate. Winey et al. explore opportunities for nanofillers to modify electrical and thermal properties of polymers. Finally, Hule and Pochan consider the opportunities of polymer nanocomposites in the medical arena.

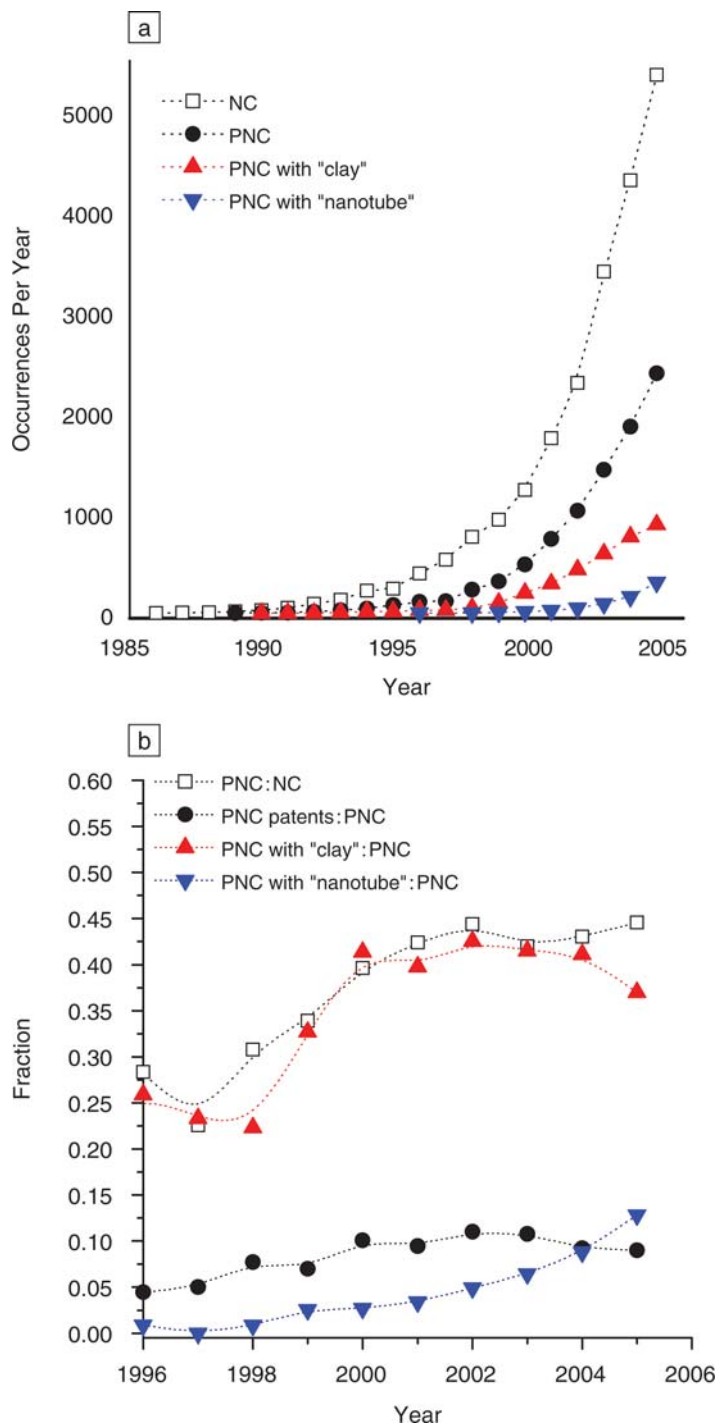


Figure 2. Growth trends of the polymer nanocomposite enterprise based on yearly publications catalogued in the CAPLUS and MEDLINE databases of the American Chemical Society.¹⁵ (a) Number of occurrences per year of the term "nanocomposite" (NC, open squares) and "nanocomposite" appearing with "polymer" (PNC, solid circles). "Polymer nanocomposites" (PNC) is further refined to those discussing "clay" PNC (red symbols) and "nanotube" PNC (blue symbols). (b) Analysis of the number of citations per year, showing the total fraction of "nanocomposite" occurrences that discuss polymer nanocomposites (PNC:NC, open squares), as well as the total fraction of "polymer nanocomposite" occurrences that are patents (PNC patents, solid circles) that discuss clay-based PNCs (PNC with "clay," red symbols) and that discuss nanotube-containing PNCs (PNC with "nanotube," blue symbols).

Future Outlook

What's next? Where are the ground-breaking opportunities? What are the challenges that pervade polymer nanocomposites? Of extreme importance in all the potential markets is the establishment of a better, quantitative understanding of the occupational health risks.³¹ For polymer nanocomposites, this is particularly important during the production of nano-sized fillers and composite fabrication, as well as during recycling, incineration, or combustion.

Whereas the recent increased availability of the new nanoscale fillers has been a major contributor to the rapid development of polymer nanocomposites, robust structure-property-processing relationships are critical to further market infiltration. Relationships that provide *a priori* predictions of macroscopic properties for a given polymer, a specific nanoscale filler (or fillers), and a particular spatial arrangement of the filler are still in their infancy. For example, to what extent can existing continuum composite theories be modified to account for the implications that arise when the filler is comparable to the polymer in size? Are the properties currently being achieved in polymer nanocomposites as high as we can expect to obtain?

However, approaches to these challenges are not without precedent. The underlying science and constitutive relationships for these nanoscopic materials should share commonality with collections of nanoscopic polymer chains, whose framework has been developed through nearly a century of chemistry and physics and is the foundation of the global polymer industry. Future developments toward the full potential of nanoscale multicomponent polymer blends rely on these previous insights to tackle the ambiguities associated with smaller filler sizes, where the distinction between filler and polymer faded into filler-molecules and polymer-molecules.

Economically, given the current diversity in nanoparticle cost (carbon black and montmorillonite versus single-wall carbon nanotubes), two approaches are developing based on potential markets. The lower-cost nanoparticles provide competition to traditional filler technologies and have important advantages in commodity applications, whereas the higher-cost nanoparticles target higher-value industrial sectors such as medical and electronics. Rather than replacing existing materials and traditional filled plastics, a common business strategy is to develop new applications based on the uniqueness of polymer nanocomposites, such as shape-memory materials for morphing aircraft, self-passivating films for satellites,

and piezoresistive materials for MEMS-based sensors. In addition, new processing tools and on-line controls are being developed to either (1) uniformly distribute nanofiller to produce homogeneous bulk properties or (2) spatially vary the nanofiller concentration to meet specific design criteria. One might refer to these two classes of polymer nanocomposites as nano-"filled" systems and nano-"composite" systems, respectively. By drawing inspiration from biology and engineered fiber-reinforced composites, polymer nanocomposites with spatially controlled morphology are beginning to provide viable options to critical components of active devices, such as fuel cell membranes, batteries, photovoltaics, sensors, and actuators.

Polymer nanocomposites have recently become part of established modern technologies, but the most significant accomplishments of these materials are still ahead of us. As an increasing number of scientists and engineers contribute to the understanding of polymer nanocomposites, what remains to be seen is which products will be critically enhanced and enabled by this broad and evolving class of materials.

Acknowledgments

The authors thank Minfang Mu (University of Pennsylvania) for compiling the data for Table I. K.I. Winey thanks Dupont for hosting her sabbatical visit and acknowledges funding from NSF-DMR-MRSEC-05-20020. R.A. Vaia thanks the Materials Research Laboratory at the University of California, Santa Barbara, for hosting his sabbatical visit.

References

1. Y. Fukushima, S. Inagaki, *J. Inclusion Phenom.* **5**, 473 (1987).
2. Y. Fukushima, A. Okada, M. Kawasumi, T. Kurauchi, O. Kamigaito, *Clays Clay Miner.* **23**, 27 (1988).
3. A. Usuki et al., *J. Mater. Res.* **8**, 1174 (1993).
4. Y. Kojima et al., *J. Mater. Res.* **8**, 1185 (1993).
5. R.A. Vaia, H. Ishii, E.P. Giannelis, *Chem. Mater.* **5**, 1694 (1993).
6. T.P. Lan, T.J. Pinnavaia, *Chem. Mater.* **6**, 2216 (1994).
7. A. McWilliams, "Nanocomposites, Nanoparticles, Nanoclays, Nanotubes" (NANO21C, BCC Research, Norwalk, CT, 2006).
8. "Polymer Nanocomposites Create Exciting Opportunities in the Plastics Industry" (Principia Partners, Jersey City, NJ, 2005).
9. A.M. Thayer, *Chem. Eng. News* **78**, 36 (October 16, 2000).
10. R.A. Vaia, E.P. Giannelis, *MRS Bull.* **26**, 394 (2001).
11. R.A. Vaia, H.D. Wagner, *Mater. Today* **7**, 32 (November 2004).

12. A. Bansal, H. Yang, C. Li, K. Cho, B.C. Benicewicz, S.K. Kumar, L.S. Schadler, *Nature Materials* **4**, 693 (2005).
13. R. Krishnamoorti, R.A. Vaia, E.P. Giannelis, *Chem. Mater.* **9**, 1728 (1996).
14. F.W. Starr, T.B. Schroeder, S.C. Glotzer, *Macromolecules* **35**, 4481 (2002).
15. SciFinder, Chemical Abstract Service (CAS) of the American Chemical Society, CAPLUS and MEDLINE databases, October 8, 2006. Data resulted from a keyword search on "nanocomposite" and selecting citations that included this concept (25,435 total citations). Results were refined using "polymer" (10,350 total citations), "nanotube or nanorod" (864 total citations), or "clay or (layered silicate) or montmorillonite" (3,938 total citations). Other keyword combinations did not drastically modify the refined number of citations (<2-3%).
16. E.P. Giannelis, *Adv. Mater.* **8**, 29 (1996).
17. M. Alexandre, P. Dubois, *Mater. Sci. Eng., R* **28**, 1 (2000).
18. S.S. Ray, M. Okamoto, *Prog. Polym. Sci.* **2**, 1539 (2003).
19. M. Okamoto, "Polymer/Clay Nanocomposites," in *Encyclopedia of Nanoscience and Nanotechnology*, H.S. Nalwa, Ed. (American Scientific, Stevenson Ranch, CA, 2004), vol. 8, p. 1.
20. E.T. Thostenson, C. Li, T.-W. Chou, *Compos. Sci. Technol.* **65**, 491 (2005).
21. L.F. Drummy, H. Koerner, B.L. Farmer, R.A. Vaia, *Advanced Morphology Characterization of Clay-Based Polymer Nanocomposites: CMS Workshop Lecture Series* (Clay Minerals Society, Chantilly, VA, 2006) vol. 14.
22. S.C. Tjong, *Mater. Sci. Eng., R* **53**, 73 (2006).
23. F. Hussain, M. Hojjati, M. Okamoto, R.E. Gorga, *J. Compos. Mater.* **40**, 1511 (2006).
24. X.-L. Xie, Y.-W. Maia, X.-P. Zhou, *Mater. Sci. Eng., R* **49**, 89 (2005).
25. M. Moniruzzaman, K.I. Winey, *Macromolecules (Review)* **39**, 5194 (2006).
26. T.J. Pinnavaia, G.W. Beall, *Polymer-Clay Nanocomposites* (Wiley, New York, 2001).
27. R. Krishnamoorti, R.A. Vaia, Eds., *Polymer Nanocomposites: Synthesis, Characterization, Modeling* (ACS Symposium Series, American Chemical Society, Washington, DC, 2001).
28. S.S. Ray, M. Bousmina, *Polymer Nanocomposites and Their Applications* (American Scientific, Stevenson Ranch, CA, 2006).
29. Y.-W. Mai, Z.-Z. Yu, Eds., *Polymer Nanocomposites CRC* (Woodhead Publishing, Cambridge, UK, 2006).
30. A.B. Morgan and C.A. Wilkie, Eds., *Flame Retardant Polymer Nanocomposites* (Wiley, New York, 2007).
31. "Environmental, Health and Safety Needs for Engineered Nanoscale Materials" (Committee on Technology, National Science and Technology Council, Washington, DC, 2006; www.nano.gov).
32. J.-B. Donnet, R.C. Bansal, M.-J. Wang, *Carbon Black* (Marcel Dekker, New York, ed. 2, 1993); J.C. Grunlan, W.W. Gerberich, L.F. Francis, *Polym. Eng. Sci.* **41**, 1947 (2001).
33. J.-B. Donnet, T.K. Wang, S. Rebouillat, J.C.M. Peng, *Carbon Fibers* (Marcel Dekker, New York, ed. 3, 1998; www.apsci.com/home.html).
34. A. Yasmin, I.M. Daniel, *Polymer* **45**, 8211 (2004); D.D.L. Chung, *J. Mater. Sci.* **37**, 1475

- (2002); J.M. Keith, C.D. Hingst, M.G. Miller, J.A. King, R.A. Hauser, *Polym. Compos.* **27**, 1 (2006).
35. D.P.N. Vlasveld, P.P. Parlevliet, H.E.N. Bersee, S.J. Picken, *Composites Part A* **36**, 1 (2005); A. Pegormti, L. Fambfu, C. Migliaresi, *Polym. Compos.* **21**, 466 (2000).
36. K. Yang et al., *Polym. Comp.* **27**, 443 (2006); M. Lei et al., *J. Cryst. Growth* **294**, 358 (2006); T. Ding, E.S. Daniels, M.S. El-Aasser, A. Klein, *J. Appl. Polym. Sci.* **100**, 4550 (2006); E. Ramachandran, P. Raji, K. Ramachandran, S. Natarajan, *Cryst. Res. Technol.* **41**, 64 (2006).
37. C. Clauser, E. Huenges, in *Rock Physics and Phase Relations: A Handbook of Physical Constants* (American Geophysical Union, Washington, DC, 1995) p. 105.
38. L. Brabec et al., *Microporous Mesoporous Mater.* **94**, 226 (2006); I. Hackman, L. Hollaway, *Composites Part A* **37**, 1161 (2006).
39. V. Svehlova, E. Poloucek, *Angew. Makromol. Chem.* **214**, 91 (1994); E. Bailey, J.R. Holloway, *Earth. Planet. Sci. Lett.* **183**, 487 (2000); A. Kirak, H. Yilmaz, S. Guler, C. Guler, *J. Phys. D: Appl. Phys.* **32**, 1919 (1999).
40. Applied Sciences Inc. Home Page, <http://www.apsci.com/home.html>; H.Y. Ng, X. Lu, S.K. Lau, *Polym. Compos.* **26**, 66 (2005); C. Yu et al., *Trans. ASME* **128**, 234 (2006); J. Zeng et al., *Composites Part B* **35**, 245 (2004); T. Morita, H. Inoue, Y. Suhara, U.S. Patent 6,565,971 (May 20, 2003).
41. J. Zeng et al., *Composites Part B* **35**, 245 (2004); NanoLab Home Page, www.nano-lab.com/nanotubes-research-grade.html; M.-K. Yeh, N.-H. Tai, J.-H. Liu, *Carbon* **44**, 1 (2006); M. Fujii et al., *Phys. Rev. Lett.* **95**, 065502 (2005); T.W. Ebbesen et al., *Nature* **382**, 54 (1996).
42. E. Bichoutskaia, M.I. Heggie, A.M. Popov, Y.E. Lozovik, *Phys. Rev. B* **73**, 045435 (2006); S. Berber, Y.-K. Kwon, D. Tománek, *Phys. Rev. Lett.* **84**, 4613 (2000); U. Dettlaff-Weglikowska et al., *J. Am. Chem. Soc.* **127**, 5125 (2005).
43. H.S. Jeona, J.K. Rameshwarama, G. Kimb, D.H. Weinkauff, *Polymer* **44**, 5749 (2003); Y.-P. Wu, Q.-X. Jia, D.-S. Yu, L.-Q. Zhang, *Polym. Test.* **23**, 903 (2004); V.V. Murashov, *J. Phys.: Condens. Matter.* **11**, 1261 (1999); T.J. Pinnavaia, G.W. Beall, *Polymer-Clay Nanocomposites*, Wiley Series in Polymer Science (Wiley, New York, 2001).
44. S. Amarchand, T.R. Rama Mohan, P. Ramakrishnan, *Adv. Powder Technol.* **11**, 415 (2000); R.J. Fleming et al., *IEEE Trans. Dielectrics and Electrical Insulation* **12**, 745 (2005); The A to Z of Materials Home Page, www.azom.com/details.asp?ArticleID1179.
45. High Precision Machining of Hard Materials, Insaco Inc. Home Page, www.insaco.com/home.asp. □



Karen I. Winey



Richard A. Vaia



Jeff Baur



Brian C. Benicewicz



Shane E. Harton

Karen I. Winey, Guest Editor for this issue of *MRS Bulletin*, is a professor of materials science and engineering at the University of Pennsylvania. She earned her BS degree in materials science and engineering from Cornell University and her MS and PhD degrees in polymer science and engineering from the University of Massachusetts under the direction of Edwin L. Thomas.

Winey probes structure-property relationships in nanotube-polymer composites, ion-containing polymers, and block copolymers, where the properties of interest include electrical conductivity, thermal conductivity, mechanical properties and permeability. She received an

NSF Young Investigator Award in 1994 and was elected fellow of the American Physical Society in 2003. Winey is currently chair of the Polymer Physics Gordon Research Conference scheduled for 2010. She recently published an invited review article entitled "Polymer Nanocomposites Containing Carbon Nanotubes" in *Macromolecules* (**39**, 5194-5205, 2006).

Winey can be reached at 3231 Walnut St., University of Pennsylvania, Philadelphia, PA 19104-6272, USA; tel. 215-898-0593, fax 215-573-2128, and e-mail winey@seas.upenn.edu.

Richard A. Vaia, Guest Editor for this issue of *MRS Bulletin*, is the lead of the

NanoMaterials Strategy Group and chair of the NanoScience and Technology (NST) Strategic Technology Team at the U.S. Air Force Research Laboratory (AFRL). He received his PhD degree in materials science and engineering at Cornell University in 1995 and was a distinguished graduate from Cornell's Air Force ROTC.

Vaia's research group focuses on polymer nanocomposites, photonic technologies, and their impact on developing adaptive soft matter. His honors and awards include Air Force Outstanding Scientist (2002); MRL Visiting Professor at the University of California, Santa Barbara (2006); Air Force Office of Scientific Research Star Team (2003-2005, 2005-2007), and the

Outstanding Engineers and Scientists Award (2006) from the Affiliate Societies Council of Dayton, Ohio. Vaia serves on the editorial boards of *Chemistry of Materials*, *Macromolecules*, and *Materials Today*. He is on the MRS board of directors, and is a member-at-large for the Division of Polymeric Materials Science and Engineering of the American Chemical Society. He has authored more than 100 papers and patents.

Vaia can be reached at the Air Force Research Laboratory, 2941 Hobson Way, Bldg. 654, Wright-Patterson Air Force Base, OH 45433-7750 USA; tel. 937-255-9184, fax 937-255-9157, and e-mail richard.vaia@wpafb.af.mil.

Jeff Baur is a senior research engineer for the Advanced Composites Branch within the Air Force Research Laboratory's Materials and Manufacturing Directorate. He received his PhD degree from the Massachusetts Institute of Technology's program in polymer science and technology in 1997.

Baur has held research and management positions within the Air Force Research Lab, Borden Chemical UV Coating Division, and at MIT's Institute for Soldier Nanotechnologies, and has published numerous papers in advanced electrical, optical, and mechanical properties of polymer composites. His current interests are in nanocomposites for improvement of fiber-reinforced



Rohan A. Hule

composite structures and materials for morphing structures.

Baur can be reached at AFRL/MLBCO, 2941 Hobson Way, Wright-Patterson Air Force Base, OH 45433-7750 USA; tel. 937-255-9143, fax 937-656-4706, and e-mail jeff.baur@wpafb.af.mil.

Brian C. Benicewicz is director of the New York State Center for Polymer Synthesis and a professor of chemistry at Rensselaer Polytechnic Institute in Troy, N.Y. He received his BS degree from the Florida Institute of Technology in 1976 and his PhD degree in polymer chemistry from the University of Connecticut in 1980.

Benicewicz held positions at Celanese Research Co. and at Johnson & Johnson and was the deputy group leader at Los Alamos National Laboratory before joining Rensselaer in 1997. His research focuses on polymer nanocomposites, controlled radical polymerizations, fuel cell membranes, liquid-crystalline and electrically conducting polymers, and polymer synthesis.

Benicewicz can be reached at the Department of Chemistry and Chemical Biology, Rensselaer Polytechnic



Douglas L. Hunter

Institute, 110 Eighth St., Troy, NY 12180 USA; tel. 518-276-2534, fax 518-276-6434, and e-mail benice@rpi.edu.

Shane E. Harton is a postdoctoral research scientist in the Department of Chemical Engineering at Columbia University, working with Sanat K. Kumar. Harton received his PhD degree in materials science and engineering from North Carolina State University in 2005 under the advisement of Harald Ade.

As a graduate student, Harton's work primarily focused on thermodynamics of highly incompatible polymer/polymer interfaces, particularly the influences of the deuterium isotope effect. Harton's current work at Columbia University focuses on thermodynamics of polymer/inorganic interfaces, including compatibilization of polymer/inorganic nanocomposites.

Harton can be reached at the Department of Chemical Engineering, Columbia University, 500 W. 120th St., New York, NY 10027 USA.

Rohan A. Hule is a graduate student in the Department of Materials Science and Engineering



Karl W. Kamena

and the Delaware Biotechnology Institute at the University of Delaware. After earning his BTech degree in polymer science and engineering from the University Institute of Chemical Technology in Mumbai, India, Hule studied rheology in the Complex Fluids and Polymer Engineering Group at the National Chemical Laboratory in Pune.

Hule's current research focuses on organic-inorganic hybrid nanomaterials, self-assembled hydrogels, and understanding structure-property relationships in bio-nanomaterials using polymer physics tools.

Hule can be reached by e-mail at hule@udel.edu.

Douglas L. Hunter is a senior scientist at Southern Clay Products Inc. (SCP), where he has worked since 1997. He earned his PhD degree in chemistry at Texas A&M University. Prior to SCP, he worked at Dow Chemical Co., beginning in 1975. At Dow, Hunter held a variety of positions working in early-stage catalyst and process development and technical service. The focus of his research at SCP has been polymer clay nanocomposites.



Takashi Kashiwagi

Hunter can be reached at Southern Clay Products, 1212 Church St., Gonzales, TX 78629 USA; tel. 830-672-1994 and e-mail dhunter@scprod.com.

Karl W. Kamena is the commercial manager of Cloisite® Nanoclays at Southern Clay Products Inc. He graduated from the University of Massachusetts in 1965 with a degree in chemical engineering.

Kamena worked with Dow Chemical Co. from 1965 to 1994 in a variety of technical and commercial positions. His experience at Dow ranged from product development and project management to business, marketing, public policy issues management, and government affairs. During the past ten years, Kamena has been involved with clay/polymer nanocomposite technologies in consulting capacities and working with companies. He is a member of the Society of Plastics Engineers.

Kamena can be reached at Cloisite® Nanoclays, 5508 Hwy. 290 West, Ste. 206, Austin, TX 78735 USA; tel. 512-358-3108, fax 512-899-2332, and e-mail kkamena@scprod.com.

Takashi Kashiwagi is a research professor in the Fire Protection Engi-



Ramanan Krishnamoorti

neering Department of the University of Maryland and a guest researcher at the Fire Research Division of the National Institute of Standards and Technology. Kashiwagi earned his BS and MS degrees from Keio University and his PhD degree from Princeton University in aerospace mechanical science. His research interests include combustion of polymeric materials and flammability properties of polymer nanocomposites.

Kashiwagi can be reached at NIST, MS 8665, 100 Bureau Dr., Gaithersburg, MD 20899-8665 USA; tel. 301-975-6699, fax 301-975-4052, and e-mail takashi.kashiwagi@nist.gov.

Ramanan Krishnamoorti is a professor of chemical and biomolecular engineering and a professor of chemistry at the University of Houston (UH). After earning his PhD degree in chemical engineering from Princeton University in 1994, he held postdoctoral positions at the California Institute of Technology and Cornell University.

Krishnamoorti joined UH as an assistant professor in 1996 and was promoted to professor and appointed associate



Sanat K. Kumar

dean for research in 2005. His primary research area is in the understanding of structure-processing-property relations for multicomponent polymeric materials, with recent extensions into biomaterials for drug delivery and the development of high-performance ceramic materials.

Krishnamoorti can be reached at the Department of Chemical Engineering, University of Houston, 4800 Calhoun Rd., Houston, TX 77204-4004 USA; tel. 772-04-4004 USA; tel. 713-743-4312, fax 713-743-4323, and e-mail ramanan@uh.edu.

Sanat K. Kumar is a professor in the Chemical Engineering Department at Columbia University. He received his BS degree from the Indian Institute of Technology, Madras, in 1981 and his PhD degree from the Massachusetts Institute of Technology in 1987. Kumar has held faculty positions at the Pennsylvania State University and Rensselaer Polytechnic Institute.

His research focuses on synthetic and bio polymers, nanocomposites, and nanomaterials. His work impacts the fields of biochemical engineering, composite materials, interfacial



Sarah L. Lewis

phenomena, nanotechnology, and polymers.

Kumar can be reached at the Department of Chemical Engineering, Columbia University, 500 W. 120th St., New York, NY 10027 USA; tel. 212-854-2193, fax 212-854-3054, and e-mail sk2794@columbia.edu.

Sarah L. Lewis is pursuing her PhD degree in materials science and engineering at Rensselaer Polytechnic Institute in Troy, N.Y. She received her MS degree in materials science and engineering from Lehigh University in 2003 and her BSc degree in biomedical materials science from the University of Manchester Institute of Science and Technology in 2001. Her research interests are in controlling and predicting properties in polymer nanocomposites.

Lewis can be reached at the Department of Materials Science and Engineering, Rensselaer Polytechnic Institute, 110 Eighth St., Troy, NY 12180 USA; tel. 518-276-3011, fax 518-276-8554, and e-mail lewiss@rpi.edu.

Minfang Mu is a PhD degree candidate in the Department of Materials Science and Engineering at the University of



Minfang Mu

Pennsylvania. She received her BSc degree in chemistry and her MSc degree in the Department of Macromolecular Science at Fudan University, China. At Fudan University, Mu worked with Ming Jiang on self-assembly of protein-graft-dextran and polymer complexes. Currently, she is working on the diffusion behavior of polymers into carbon nanotube/polymer nanocomposites, as well as the preparation and characterization of composites with cellular nanotube networks.

Mu can be reached at the University of Pennsylvania, 3231 Walnut St., Philadelphia, PA 19104-6272, USA; tel. 215-898-2700 and e-mail minfang@seas.upenn.edu.

Donald R. Paul holds the Ernest Cockrell Sr. Chair in Engineering at the University of Texas at Austin and also is the director of the Texas Materials Institute. He joined the Department of Chemical Engineering at UT in 1967. Paul's research interests include polymer blends, membranes, processing, and nanocomposites. He was elected to the National Academy of Engineering in 1988 and to the Mexican Academy of Sciences in 2000, and



Donald R. Paul

has served as editor of *Industrial and Engineering Chemistry Research*, published by the American Chemical Society, since 1986.

Paul can be reached at the Department of Chemical Engineering, University of Texas at Austin, Austin, TX 78712 USA; tel. 512-471-5392, fax 512-471-0542; and e-mail drp@che.utexas.edu.

Darrin J. Pochan is an associate professor in the Materials Science and Engineering Department and the Delaware Biotechnology Institute at the University of Delaware. He joined the department in 1999 after earning his PhD degree in polymer science and engineering at the University of Massachusetts Amherst and having an NRC postdoctoral fellowship at the National Institute of Standards and Technology.

At the University of Delaware, Pochan has developed a research program around the construction of new materials and nanostructures via molecular self-assembly mechanisms. His recent honors include an NSF Career Award, the DuPont Young Faculty Award, and the Dillon Medal from the American Physical Society. Pochan



Darrin J. Pochan

also serves as associate editor for *North America of Soft Matter*, a new interdisciplinary journal from the Royal Society of Chemistry.

Pochan can be reached by e-mail at poch@udel.edu.

Linda S. Schadler is a professor in materials science and engineering at Rensselaer Polytechnic Institute. She graduated from Cornell University in 1985 with a BS degree in materials science and engineering and received a PhD degree in materials science and engineering in 1990 from the University of Pennsylvania. Schadler joined Rensselaer in 1996.

She is a current member of the National Materials Advisory Board, and in addition to her research focus on interfaces in nanocomposites, she is the education and outreach coordinator for the NSF-funded Center for Directed Assembly of Nanostructures, headquartered at Rensselaer.

Schadler can be reached at the Department of Materials Science and Engineering, Rensselaer Polytechnic Institute, 110 Eighth St., Troy, NY 12180 USA; tel. 518-276-2022, fax 518-276-8554, and e-mail schadl@rpi.edu.



Linda S. Schadler

Edward Silverman is the advanced technology manager for advanced materials



Edward Silverman

development at Northrop Grumman Space Technology. He holds a BE degree in

chemical engineering from City College of New York and a PhD degree in chemical engineering from Stanford University.

Silverman has led the development of new lightweight composite resin transfer-molded joints, isogrid reflectors, and the thermally conductive material APG (annealed pyrolytic graphite). As the program manager of two NASA contracts, he compiled two handbooks on design guide-

lines for composite spacecraft components and on space environment effects on spacecraft materials. Silverman's current interest includes the development of nanotechnology for aerospace applications. He has published more than 50 papers in scientific journals and conferences and has received several awards for innovative research and development.

Silverman can be reached at Northrop

Grumman Space Technology, One Space Park, M/S 01/2040, Redondo Beach, CA 90278 USA; tel. 310-813-9374, fax 310-812-8768, and e-mail edward.silverman@ngc.com. □

www.mrs.org/bulletin

MRS members can access full issues of *MRS Bulletin*, with additional theme-related resources, online.

www.mrs.org/alerts

MRS Publications Alert: Receive advance Table of Contents by e-mail.

The Materials Gateway—www.mrs.org

Setting New Standards in GPC

More than twenty years ago Viscotek revolutionized GPC detection with the introduction of the four-capillary differential viscometer detector. Since that time we have continued to set the standard in GPC with innovative and unique products like the Integrated Triple and Tetra Detector Array's (TDA's), the GPCmax™ Integrated Pump / Autosampler / Degasser Module, OmniSEC™ software and Complete GPC/SEC Advanced Detector Systems.

In a single experiment, our technologies make it possible to obtain absolute molecular weight, molecular size and intrinsic viscosity distributions, as well as information on structure, conformation, aggregation, branching and copolymer and conjugate composition for natural and synthetic polymers, copolymers, proteins, protein conjugates and excipients.

Viscotek is proud to once again set a new standard in GPC!

Introducing the Model 350 HTGPC, a revolutionary new generation of High Temperature GPC that represents a breakthrough in characterization technology. The 350 HTGPC features:

- Modular component design with a removable detector module for easy maintenance.
- Advanced detection with built-in LALS/RALS Light Scattering Detector and Four-capillary Differential Viscometer.
- Automated sample preparation and delivery with the Vortex Autosampler/Autopreparation Module.
- Self-cleaning in-line sample filtration with proprietary back-flush valve design.



www.viscotek.com

Viscotek

800-375-5966